


Article

# CO<sub>2</sub> electroreduction to multicarbon products from carbonate capture liquid

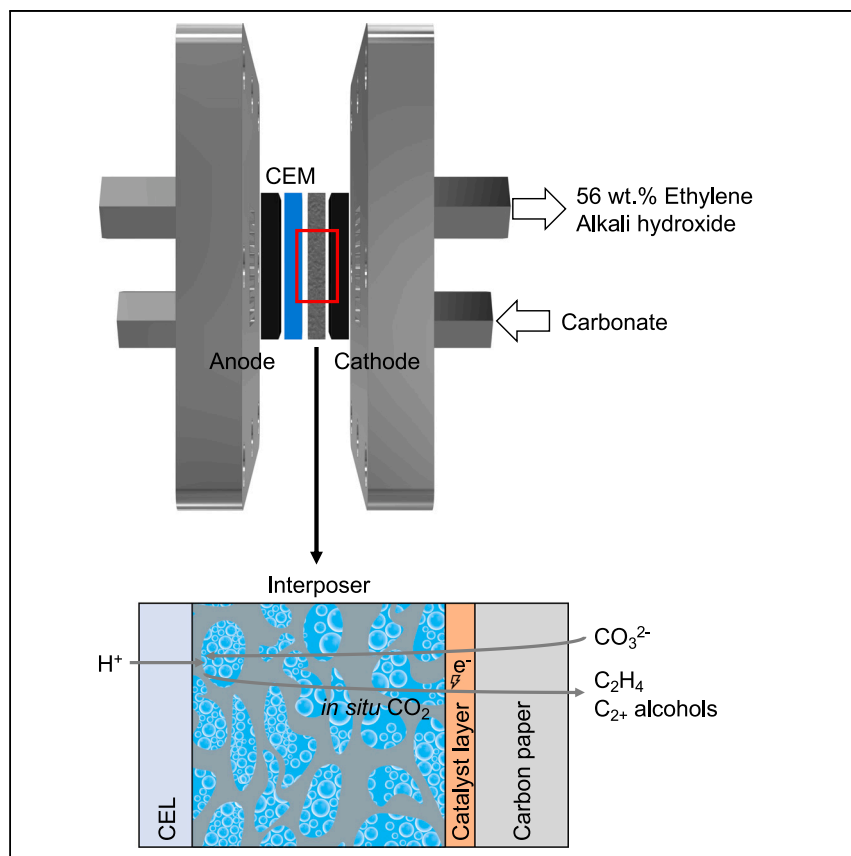

Reactive capture systems unite CO<sub>2</sub> capture with CO<sub>2</sub> upgrade/utilization into more valuable chemicals. We, herein, present the direct electrochemical upgrade of carbonate, captured CO<sub>2</sub> in direct air capture, into C<sub>2</sub> and higher products (C<sub>2+</sub>). Interposer and catalyst joint design enables us to electroproduce 56 wt % C<sub>2</sub>H<sub>4</sub> from a carbonate solution with no detected CO<sub>2</sub> in the gas stream. The carbonate electrolysis system produces a gas stream that is undiluted by CO<sub>2</sub> and accomplishes complete CO<sub>2</sub> utilization, reducing regeneration/separation costs.

Geonhui Lee, Armin Sedighian Rasouli, Byoung-Hoon Lee, ..., Zhu Chen, David Sinton, Edward Sargent

ted.sargent@northwestern.edu

Highlights

The electrochemical upgrade of CO<sub>2</sub> captured in the carbonate form to C<sub>2+</sub> products

Studying key metrics (local pH and reactant concentration) in reactive capture

Interposer and catalyst joint design enables the electroproduction of 56 wt % C<sub>2</sub>H<sub>4</sub>

Reactive capture obviates the need for energy to regenerate lost/unreacted CO<sub>2</sub>

Article

# CO<sub>2</sub> electroreduction to multicarbon products from carbonate capture liquid

Geonhui Lee,<sup>1,6</sup> Armin Sedighian Rasouli,<sup>1,6</sup> Byoung-Hoon Lee,<sup>1,6</sup> Jinqiang Zhang,<sup>1</sup> Da Hye Won,<sup>2</sup> Yuroo Celine Xiao,<sup>3</sup> Jonathan P. Edwards,<sup>3</sup> Mi Gyoungh Lee,<sup>1</sup> Eui Dae Jung,<sup>1</sup> Fatemeh Arabyarmohammadi,<sup>3</sup> Hengzhou Liu,<sup>4,5</sup> Ivan Grigioni,<sup>1</sup> Jehad Abed,<sup>1</sup> Tartela Alkayyali,<sup>3</sup> Shijie Liu,<sup>3</sup> Ke Xie,<sup>1</sup> Rui Kai Miao,<sup>3</sup> Sungjin Park,<sup>1</sup> Roham Dorakhan,<sup>1</sup> Yong Zhao,<sup>3</sup> Colin P. O'Brien,<sup>3</sup> Zhu Chen,<sup>1</sup> David Sinton,<sup>3</sup> and Edward Sargent<sup>1,4,5,7,\*</sup>

## SUMMARY

Alkali hydroxide systems capture CO<sub>2</sub> as carbonate; however, generating a pure CO<sub>2</sub> stream requires significant energy input, typically from thermal cycling to 900°C. What is more, the subsequent valorization of gas-phase CO<sub>2</sub> into products presents additional energy requirements and system complexities, including managing the formation of (bi)carbonate in an electrolyte and separating unreacted CO<sub>2</sub> downstream. Here, we report the direct electrochemical conversion of CO<sub>2</sub>, captured in the form of carbonate, into multicarbon (C<sub>2+</sub>) products. Using an interposer and a Cu/CoPc-CNTs electrocatalyst, we achieve 47% C<sub>2+</sub> Faradaic efficiency at 300 mA cm<sup>-2</sup> and a full cell voltage of 4.1 V. We report 56 wt % of C<sub>2</sub>H<sub>4</sub> and no detectable C<sub>1</sub> gas in the product gas stream: CO, CH<sub>4</sub>, and CO<sub>2</sub> combined total below 0.9 wt % (0.1 vol %). This approach obviates the need for energy to regenerate lost CO<sub>2</sub>, an issue seen in prior CO<sub>2</sub>-to-C<sub>2+</sub> reports.

## INTRODUCTION

CO<sub>2</sub> capture from air and oceans, when combined with an upgrade into chemicals that serve as precursors to long-lived materials, offers to contribute carbon-negative (cradle-to-gate) solutions that offset difficult-to-abate emissions on the path to net-zero emissions.<sup>1–3</sup> Reactive capture systems unite CO<sub>2</sub> capture with CO<sub>2</sub> upgrade/utilization into more valuable chemicals. Much progress has been made electrochemically generating CO from captured CO<sub>2</sub>, on the path to fuels and chemicals via syngas processes.<sup>4–8</sup> In thermochemistry, reactive capture has proceeded to methane, methanol, and formate.<sup>9–11</sup>

C<sub>2</sub> and higher products (C<sub>2+</sub>) represent a large global market: ethylene and ethanol lie in the range of ~US\$230B and ~US\$160B, respectively,<sup>12,13</sup> in contrast with the C<sub>1</sub> chemicals (CO and formic acid) generated by reactive capture to date, whose combined values are below US\$12B.<sup>14,15</sup> Yet, to date, it is mainly C<sub>1</sub> products that have been produced in reactive capture systems of both electrochemical and thermochemical types.

Direct air capture (DAC) using alkali hydroxide captures CO<sub>2</sub> as carbonate and generates a pure/concentrated gas-phase CO<sub>2</sub> stream via thermal swing at ~900°C.<sup>16</sup> The subsequent valorization of gas-phase CO<sub>2</sub> into value-added products

## CONTEXT & SCALE

Cradle-to-gate carbon-negative technologies, including direct air capture (DAC), have shown promise in mitigating CO<sub>2</sub> emissions. However, these emerging technologies to capture CO<sub>2</sub> from the air rely on a thermal swing to release concentrated CO<sub>2</sub>, and today this comes at a high energy cost. The ensuing step in gas-phase CO<sub>2</sub> electrolysis requires additional energy. Furthermore, this step suffers from incomplete CO<sub>2</sub> conversion. This leads to a high cost to regenerate/separate (otherwise-lost/unreacted) CO<sub>2</sub>.

To tackle these challenges, a scheme known as reactive capture has been proposed: the integrated systems for capture-and-upgrade of CO<sub>2</sub> to valuable products. This approach is the direct conversion of chemisorbed CO<sub>2</sub> into value-added products. The benefits of reactive capture are (1) to avoid the energy-intensive and carbon-positive steps associated with concentrating CO<sub>2</sub> and (2) to enable ~0% reactant losses. This obviates the need for energy to regenerate/separate lost/unreacted reactants.

introduces further energy losses and system complexity. This approach involves introducing CO<sub>2</sub> in the gas phase for electrolysis.

In contradistinction, reactive capture takes the carbon source from carbonate species, bypassing CO<sub>2</sub> concentrating steps. In prior reports of reactive capture from carbonate, Li et al. demonstrated pure syngas production with Faradaic efficiency (FE) of ~30% CO and ~70% H<sub>2</sub>, and with a Cu electrocatalyst, ~14% C<sub>2</sub> FE was observed.<sup>5</sup> The authors reported no appreciable loss of CO<sub>2</sub> during carbonate electrolysis. Such prior studies offer a path to avoid the energy-intensive steps associated with concentrating CO<sub>2</sub> and regenerating lost CO<sub>2</sub>; however, until now, the selectivity toward more valuable CO<sub>2</sub>-derived products has been limited compared with the diversity of products available in electrochemical CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR) systems.

Such electrochemical CO<sub>2</sub>RR systems, although they have achieved impressive increases in performance,<sup>17,18</sup> suffer—in the case of alkaline and neutral CO<sub>2</sub>RR—from low CO<sub>2</sub> utilization (the fraction of input CO<sub>2</sub> converted into desired products) that is ≤25% in the case of C<sub>2</sub> production due to carbonate formation in locally alkaline conditions.<sup>19</sup> The low CO<sub>2</sub> utilization leads to a high cost to regenerate (otherwise-lost/emitted) CO<sub>2</sub>.<sup>19,20</sup> Enticingly, recent studies have overcome this CO<sub>2</sub> utilization limit via local CO<sub>2</sub> regeneration<sup>21–23</sup>; however, until now, the product gas stream has still been diluted by unreacted CO<sub>2</sub> and gas-phase CO<sub>2</sub>-derived products such as carbon monoxide and methane.<sup>22,24,25</sup> Even in systems that achieved >76% CO<sub>2</sub> utilization via local CO<sub>2</sub> regeneration, unreacted CO<sub>2</sub> remains >56 wt % (Table 1).

Since CO<sub>2</sub> separation is an energy-intensive process (2–4.4 GJ/tonne of CO<sub>2</sub>),<sup>16,26,27</sup> unreacted CO<sub>2</sub> significantly increases overall system energy requirements. Eliminating CO<sub>2</sub> at the downstream could lead to a lower cost of purification demand.<sup>20,28</sup>

Here, we pursue C<sub>2+</sub> products from carbonate solution—a liquid used in DAC—in an electrochemical reactive capture system. Among the striking results is a negligible presence (sub 1%) of CO<sub>2</sub> and C<sub>1</sub> gas products such as CO and CH<sub>4</sub> in the electrolyzer outlet, a finding promising for the minimization of product separation costs.

## RESULTS

### Modeling of carbonate electrolysis

In prior reports of reactive capture from carbonate,<sup>5</sup> *in situ* CO<sub>2</sub> is regenerated via an acid/base reaction between carbonate and protons. Protons come from the cation-exchange layer (CEL) of a bipolar membrane (BPM) under reverse bias. The *in situ* CO<sub>2</sub> is converted to CO<sub>2</sub>-derived products at the surface of a Cu electrocatalyst, with C<sub>2</sub> (e.g., to ethylene and ethanol) selectivity totaling below 14% (Figure S1).

We used modeling of chemical species generation, consumption, and diffusion to seek an explanation of why C<sub>2+</sub> productivity is low in prior reactive capture studies and to identify system architectures to increase it (Figure 1B; Notes S1 and S2). The modeling results show that the spacing between the CEL of BPM and the electrocatalyst influences species concentrations in the reactive capture system (Figures S2–S6). The concentrations of CO<sub>3</sub><sup>2-</sup>, *in situ* CO<sub>2</sub>(g), and CO<sub>2</sub>(aq) vary in the spacing where the local pH changes, and the distance of spacing is the most significant descriptor for the concentration of reactant, *in situ* CO<sub>2</sub>(g).

In a prior study,<sup>5</sup> at a CEL:catalyst spacing of ~60 μm (Figures 1F, 1G, and S7), the volume fraction of CO<sub>2</sub>(g) ([CO<sub>2</sub>(g)]) at the plane of the catalyst was found to be

<sup>1</sup>Department of Electrical and Computer Engineering, University of Toronto, 35 St George Street, Toronto, ON M5S 1A4, Canada

<sup>2</sup>Clean Energy Research Center, Korea Institute of Science and Technology (KIST), Seoul 02792, Republic of Korea

<sup>3</sup>Department of Mechanical and Industrial Engineering, University of Toronto, 5 King's College Road, Toronto, ON M5S 3G8, Canada

<sup>4</sup>Department of Chemistry, Northwestern University, Evanston, IL 60208, USA

<sup>5</sup>Department of Electrical and Computer Engineering, Northwestern University, Evanston, IL 60208, USA

<sup>6</sup>These authors contributed equally

<sup>7</sup>Lead contact

\*Correspondence:  
[ted.sargent@northwestern.edu](mailto:ted.sargent@northwestern.edu)  
<https://doi.org/10.1016/j.joule.2023.05.003>

**Table 1. Energy analysis of different systems: alkaline CO<sub>2</sub>RR, neutral CO<sub>2</sub>RR, acidic CO<sub>2</sub>RR, and carbonate electrolysis**


System	Alkaline CO <sub>2</sub> RR	Neutral CO <sub>2</sub> RR	Acidic CO <sub>2</sub> RR	Carbonate electrolysis
Full cell voltage (V)	2.4	3.9	3.4	4.1
C <sub>2</sub> H <sub>4</sub> selectivity (%)	70	66	24	34
Current density (mA cm <sup>-2</sup> )	150	315	200	300
Energy efficiency (%)	34	19	8	10
CO <sub>2</sub> utilization (%)	5	11	76	100 <sup>a</sup>
C <sub>2</sub> H <sub>4</sub> concentration at the outlet (wt %)	4	8	19	56
CO <sub>2</sub> concentration at the outlet (wt %)	93	88	56	0
<b>Energy cost (GJ/tonne of C<sub>2</sub>H<sub>4</sub>)</b>				
Upstream generation	28	28	28	3
Electrolysis	142	244	586	499
Product separation	115	55	18	2
Anode separation	0	57	0	0
Carbonate generation	198	0	0	0
Total	483	384	631	504

<sup>a</sup>No detectable CO<sub>2</sub> gas in the cathodic/anodic tail gas.

~2 vol % with balanced gases of H<sub>2</sub> and C<sub>2</sub>H<sub>4</sub> at current densities of 200–350 mA cm<sup>-2</sup> (Figure 1C)—yet [CO<sub>2</sub>(g)] is required to rise above 4 vol % at the catalyst to reach a meaningful conversion rate of C<sub>2+</sub> partial current densities of 100+ mA cm<sup>-2</sup> (Notes S3 and S4; Figure S8).

We studied these effects further, noting that if the CEL and the catalyst are closely spaced (Figures 1D and 1E), the local pH at the CEL goes only as low as pH 10, and CO<sub>3</sub><sup>2-</sup> and OH<sup>-</sup> diffusion neutralize the acidic CEL surface,<sup>29,30</sup> leading to no *in situ* CO<sub>2</sub>(g) generation at applied current densities of 200–350 mA cm<sup>-2</sup> (Figure S9). By contrast, when we varied the CEL:catalyst spacing over the range 100–300 μm (Figures 1H–1K), we noted the opportunity to achieve the desired conditions of low pH (<4) at the CEL for *in situ* CO<sub>2</sub>(g) generation and [CO<sub>2</sub>(g)] > 4 vol % at the catalyst layer (CL) to trigger CO<sub>2</sub>RR toward C<sub>2+</sub> production. At the CL, the pH is above 13 since hydroxide ions are produced from CO<sub>2</sub>RR. This high local pH accelerated the C–C coupling needed for C<sub>2+</sub> to dominate over C<sub>1</sub>.<sup>31,32</sup> The pH gradient was measured using pH-sensitive dyes (Note S5). We observed a progressive pH increase from pH ~2 at the CEL surface to ~12 at the edge of the interposer in the system designed for the experimental study of pH.

For the spacing range of 130–270 μm, optimal conditions, including [CO<sub>2</sub>(g)] > 4 vol % and the desired local pH, were achieved at the current density range 250–350 mA cm<sup>-2</sup>, a regime of applied interest.<sup>33,34</sup> In the case wherein the amount of carbonate is limited due to a small spacing, such as <130 μm, there is no increase in the *in situ* CO<sub>2</sub>(g) concentration at higher current densities (Figure S3). However, the current density influences the rate of proton diffusion through the CEL: more protons diffuse at higher current densities and *in situ* CO<sub>2</sub>(g) generally increases (Figure 1C). Increasing the spacing to >130 μm promotes carbonate-rich conditions, which provide more opportunities for protons to react with carbonate (Figures S4 and S5). However, [CO<sub>2</sub>(g)] decreases at a spacing >540 μm due to an increased possibility of *in situ* CO<sub>2</sub> capture over long distances in the layer (Figure S6).

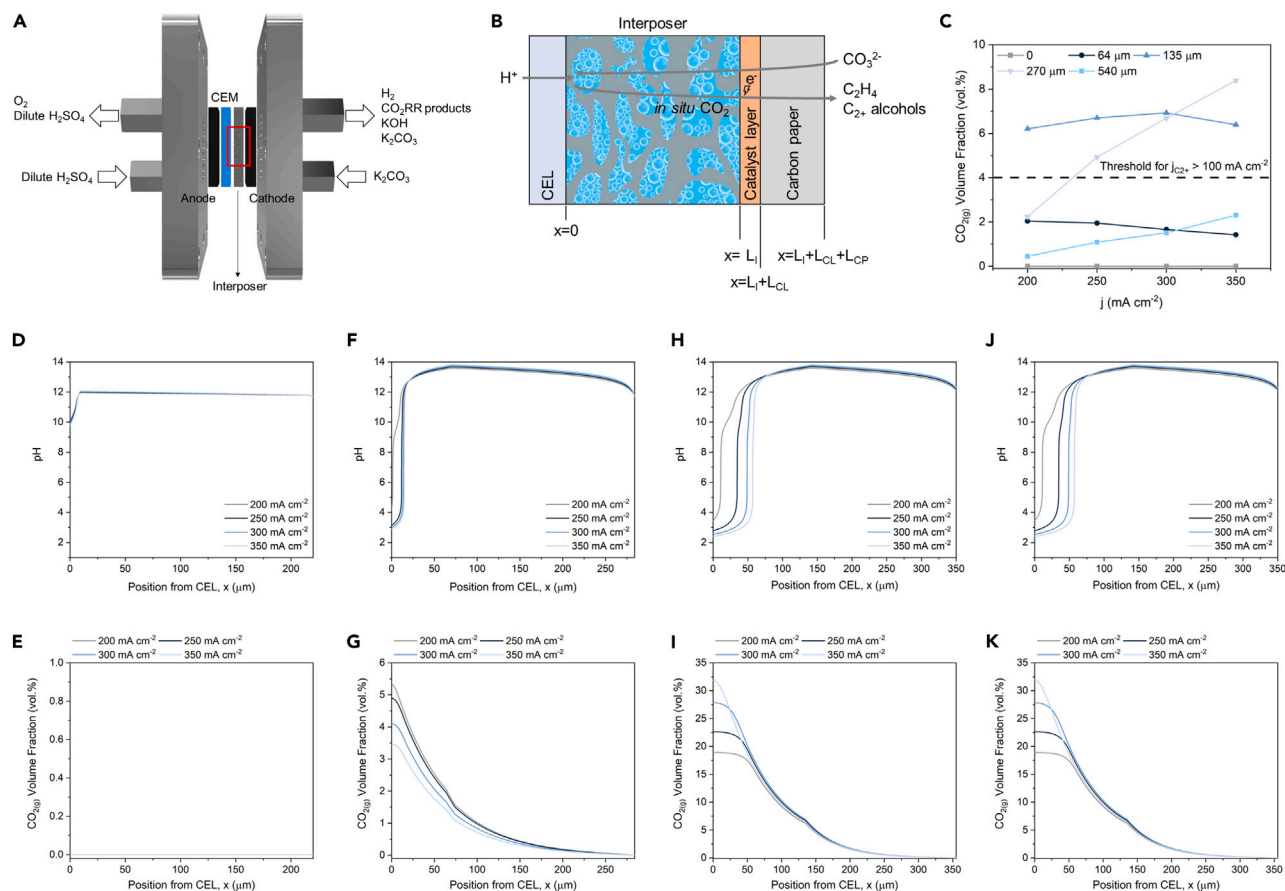


**Figure 1. Carbonate electrolysis system employing an interposer**

(A) System diagram of CO<sub>3</sub><sup>2-</sup>-fed electrolyzer. The cathode and anode are separated by the cation-exchange membrane (CEM) and the mixed cellulose ester (MCE) membrane as the interposer. K<sub>2</sub>CO<sub>3</sub> is fed to the electrolyzer, and *in situ* CO<sub>2</sub> is converted into CO<sub>2</sub>-derived products. KOH is generated at the cathode from *in situ* CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR). 0.5 M H<sub>2</sub>SO<sub>4</sub> is fed at the anode, and the anodic oxygen evolution reaction supplies protons. (B) Schematic of cation-exchange layer (CEL), the interposer, catalyst layer (CL), and carbon paper (CP). The MCE membrane has a pore where the carbonate liquid-phase and gas-phase *in situ* CO<sub>2</sub> are distributed. (C) CO<sub>2</sub>(g) volume fraction for different spacing (L) conditions, 0, 64, 135, and 540 μm at current densities of 200, 250, 300, and 350 mA cm<sup>-2</sup> in 1.5 M of K<sub>2</sub>CO<sub>3</sub> electrolyte. (D, F, H, and J) pH profile of 0, 64, 135, and 540 μm spacing, respectively, at the applied current densities from 200 to 350 mA cm<sup>-2</sup> in 1.5 M of K<sub>2</sub>CO<sub>3</sub> electrolyte. (E, G, I, and K) *In situ* CO<sub>2</sub>(g) volume fraction profile of 0, 64, 135, and 540 μm spacing, respectively, at the applied current densities from 200 to 350 mA cm<sup>-2</sup> in 1.5 M K<sub>2</sub>CO<sub>3</sub> electrolyte.

### Carbonate electrolysis system employing an interposer

We then turned to the experimental implementation of these concepts (Figure 1A). We needed an approach to construct a well-defined spacing—in effect, a stand-off—between the CEL and electrocatalyst. We used a hydrophilic membrane as an interposer and explored different interposer material compositions (Note S6; Figures S10–S12). We observed that C<sub>2+</sub> FE was improved in a higher porosity system. We account for these observations via faster diffusion of species which enabled a higher concentration of CO<sub>2</sub>(g) at the CL.

In light of these findings, we focused on a hydrophilic mixed cellulose ester (MCE) interposer, a highly porous medium (material porosity > 84%) with a selection of thicknesses ranging from 130 to 540 μm (Figure S13). We then moved to a cation-exchange membrane (CEM) in the system to transport protons from the anodic oxygen

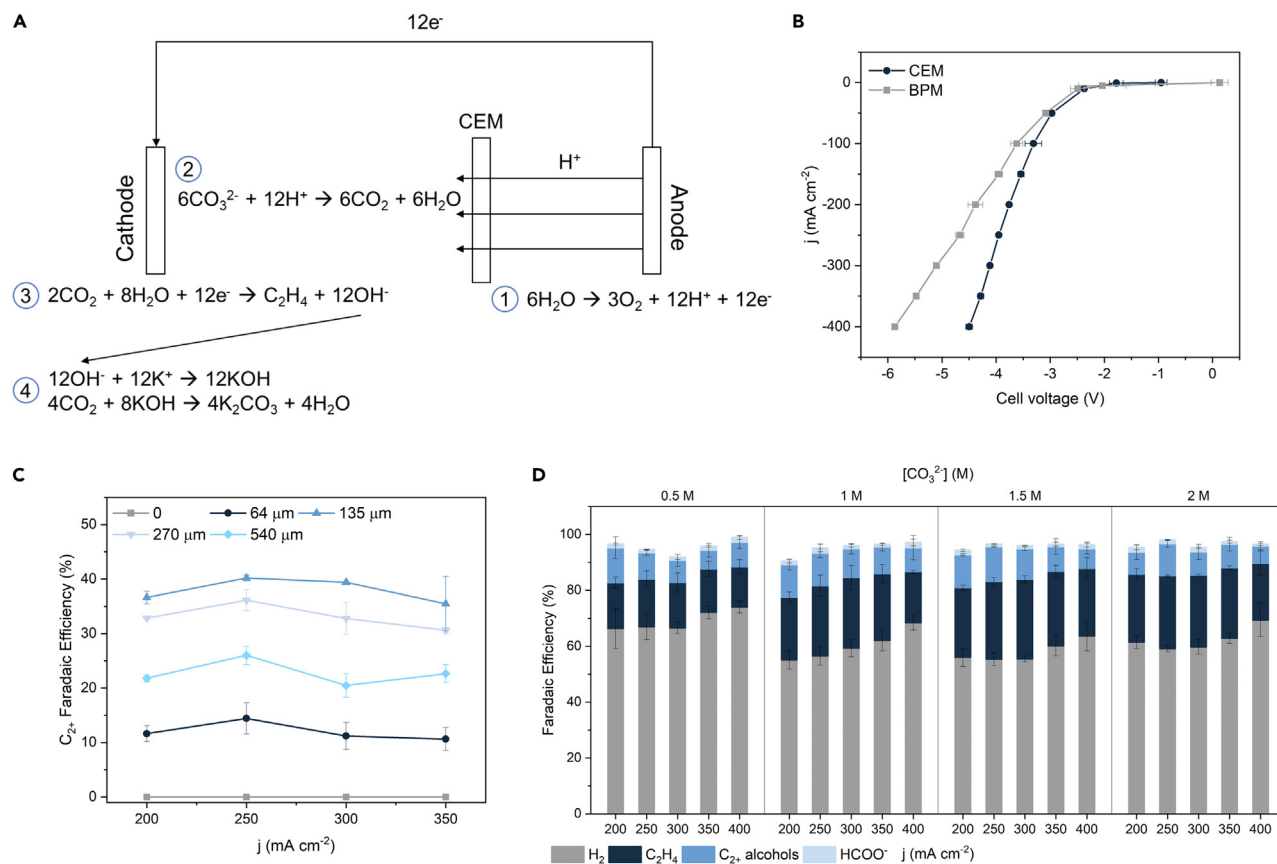

**Figure 2. Carbonate electrolysis**

(A) Chemical reactions of carbonate electrolysis with the cation-exchange membrane (CEM). OER at the anodic side supplies protons to the cathodic side. Carbonate is converted into *in situ* CO<sub>2</sub> via the carbonate/proton reactions. CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR) occurs with a Cu electrocatalyst. CO<sub>2</sub>-derived products are generated, and OH<sup>-</sup> is produced during *in situ* CO<sub>2</sub>RR. Unreacted CO<sub>2</sub> is captured by OH<sup>-</sup>.

(B) Full cell J-V curve with Cu electrocatalyst with a CEM and a bipolar membrane (BPM) in 1.5 M of K<sub>2</sub>CO<sub>3</sub> electrolyte with 135 μm interposer. Higher voltage is observed in the case of the BPM system compared with the CEM system due to water dissociation overpotential. All experiments were repeated three times to enable reporting of the average and standard error.

(C) C<sub>2+</sub> Faradaic efficiency (FE) of carbonate electrolysis with Cu electrocatalyst in 1.5 M of K<sub>2</sub>CO<sub>3</sub> electrolyte with the different thickness of interposer from 0 to 540 μm. All experiments were repeated three times to enable reporting of the average and standard error.

(D) Product distribution for different concentrations of K<sub>2</sub>CO<sub>3</sub> electrolyte from 0.5 to 2 M with a 135 μm interposer. C<sub>2+</sub> alcohols Faradaic efficiency includes C<sub>2</sub>H<sub>5</sub>OH and C<sub>3</sub>H<sub>7</sub>OH. All experiments were repeated three times to enable reporting of the average and standard error.

evolution reaction (OER) (Figure 2A)—an improvement that enabled reduced full cell potential compared with a BPM system (Figure 2B). The CEM system may supply more protons to the cathodic side than the BPM system due to the concentration gradient, neutralizing the capture species (OH<sup>-</sup>). However, we observed a similar product distribution for both the BPM system and CEM system (Figure S14), indicating that excess proton diffusion in the CEM system is negligible when using 0.5 M H<sub>2</sub>SO<sub>4</sub> as an anolyte (Note S7).

Experimentally, we first reconfirmed the findings of prior studies that, at ~60 μm spacing, FE to C<sub>2+</sub> resides below 14% at 250 mA cm<sup>-2</sup>. When we optimized interposer thickness of 130–270 μm, we achieved a much-increased C<sub>2+</sub> FE of 40% at 250 mA cm<sup>-2</sup> (Figure 2C). When the distance is smaller than 135 μm or larger than 540 μm, a lower rate of C<sub>2+</sub> product generation is seen, the result of the limited concentration of *in situ* CO<sub>2</sub>(g) (Figure 1C). In all cases, the only C<sub>1</sub> product detected was HCOO<sup>-</sup> with FE below 2%. No CO, CH<sub>4</sub>, and CO<sub>2</sub> were detected for all applied

current densities and different concentrations of carbonate electrolyte in the interposer system (Figures 2D and S11). The product distribution, including high C<sub>2+</sub> FE and negligible CO FE, was also observed in a simulated carbonate electrolysis system with CO<sub>2</sub>-depleted conditions (Note S3). The experimental studies suggest that in the carbonate electrolysis system, low [CO<sub>2</sub>(g)] and slow *in situ* CO<sub>2</sub> flux contribute to steering C–C coupling by achieving locally concentrated CO and the enhanced residence time of CO. In the outlet stream, gaseous C<sub>1</sub> products and CO<sub>2</sub> were <0.9 wt % (0.1 vol %) based on the detection limit of the gas chromatography (GC): CO for 24 ppm, CH<sub>4</sub> for 56 ppm, and CO<sub>2</sub> for 1,000 ppm, respectively (experimental procedures). To investigate whether carbonate was the source of carbon in electroreduction, we used <sup>13</sup>C labeled CO<sub>3</sub><sup>2-</sup>, and the isotope experiment result ruled out any chemical reactions of interposer, cathode, and dissolved CO<sub>2</sub> (Figure S15). To test for the possibility of chemical reactions related to the MCE membrane or its possible decomposition products, we compared electrochemical performance in two conditions: (1) carbonate electrolyte and (2) carbonate electrolyte with a dispersed MCE membrane in a PVDF interposer system (Figure S16). In both cases, we observed a C<sub>2+</sub> FE of ~15% at the applied current density of 200 and 300 mA cm<sup>-2</sup>. We also conducted nuclear magnetic resonance (NMR) analysis to examine the chemical decomposition of the MCE membrane after long-term electrolysis of carbonate. We only detected signals for CO<sub>2</sub>-derived products, which supports that there is no chemical decomposition or reactions of MCE in the carbonate electrolysis system (Figure S17).


### Improved catalyst for carbonate electrolysis

We turned to further system tuning toward increased C<sub>2+</sub> FE. We posited that a portion of *in situ* CO<sub>2</sub> is converted into CO<sub>3</sub><sup>2-</sup> at the catalyst surface due to the highly alkaline conditions.<sup>31</sup> We, therefore, sought catalyst-design strategies to convert CO<sub>2</sub> to CO with faster kinetics at the catalyst surface to preserve the reactant. We used molecularly dispersed cobalt phthalocyanines on carbon nanotubes (CoPCs-CNTs) known to produce CO from CO<sub>2</sub> with high turnover frequencies (Figure 3A).<sup>35,36</sup> We fabricated the layer-by-layer catalyst via airbrushing. The CoPC-CNTs layer is uniformly distributed on the Cu layer as shown in the scanning electron microscopy (SEM) image (Figure 3B). X-ray photoelectron spectroscopy (XPS) and energy-dispersive X-ray spectroscopy (EDS) confirm the existence of cobalt at the surface (Figures S18 and S19).

The product distribution now showed a considerable further improvement: the C<sub>2+</sub> total FE now rose to 47% at 300 mA cm<sup>-2</sup> (Figure 3C). The C<sub>2</sub>H<sub>4</sub> FE is 34%, resulting in 56 wt % of C<sub>2</sub>H<sub>4</sub> in the product gas stream due to the absence of gaseous C<sub>1</sub> products and unreacted CO<sub>2</sub>. The C<sub>2+</sub> alcohols FE is 13% including 12% C<sub>2</sub>H<sub>5</sub>OH FE and 1% C<sub>3</sub>H<sub>7</sub>OH FE. As shown in Figure 3D, we achieve 140+ mA cm<sup>-2</sup> of C<sub>2+</sub> partial current density at -4.1 V.

### Continuous operation of capture-and-electrolysis system

We then constructed a prototype that operates both CO<sub>2</sub> capture and electrolysis on a continuous basis (Figures 4A and S20). The KOH capture liquid is regenerated during carbonate electrolysis as shown in the chemical balance (Figure 2A; Note S7). We recycled the resultant KOH solution to continuously capture additional CO<sub>2</sub>, converting it into K<sub>2</sub>CO<sub>3</sub>. There are two reservoirs: the absorber is for CO<sub>2</sub> capture and the electrolyte reservoir provides the carbonate to the liquid-fed electrolyzer. Two reservoirs and the electrolyzer are connected by peripheral pumps circulating the capture liquid. During the electrolysis of carbonate into C<sub>2</sub>H<sub>4</sub> and C<sub>2+</sub> alcohols, generated OH<sup>-</sup> returns to the absorber. We demonstrated capture-and-electrolysis

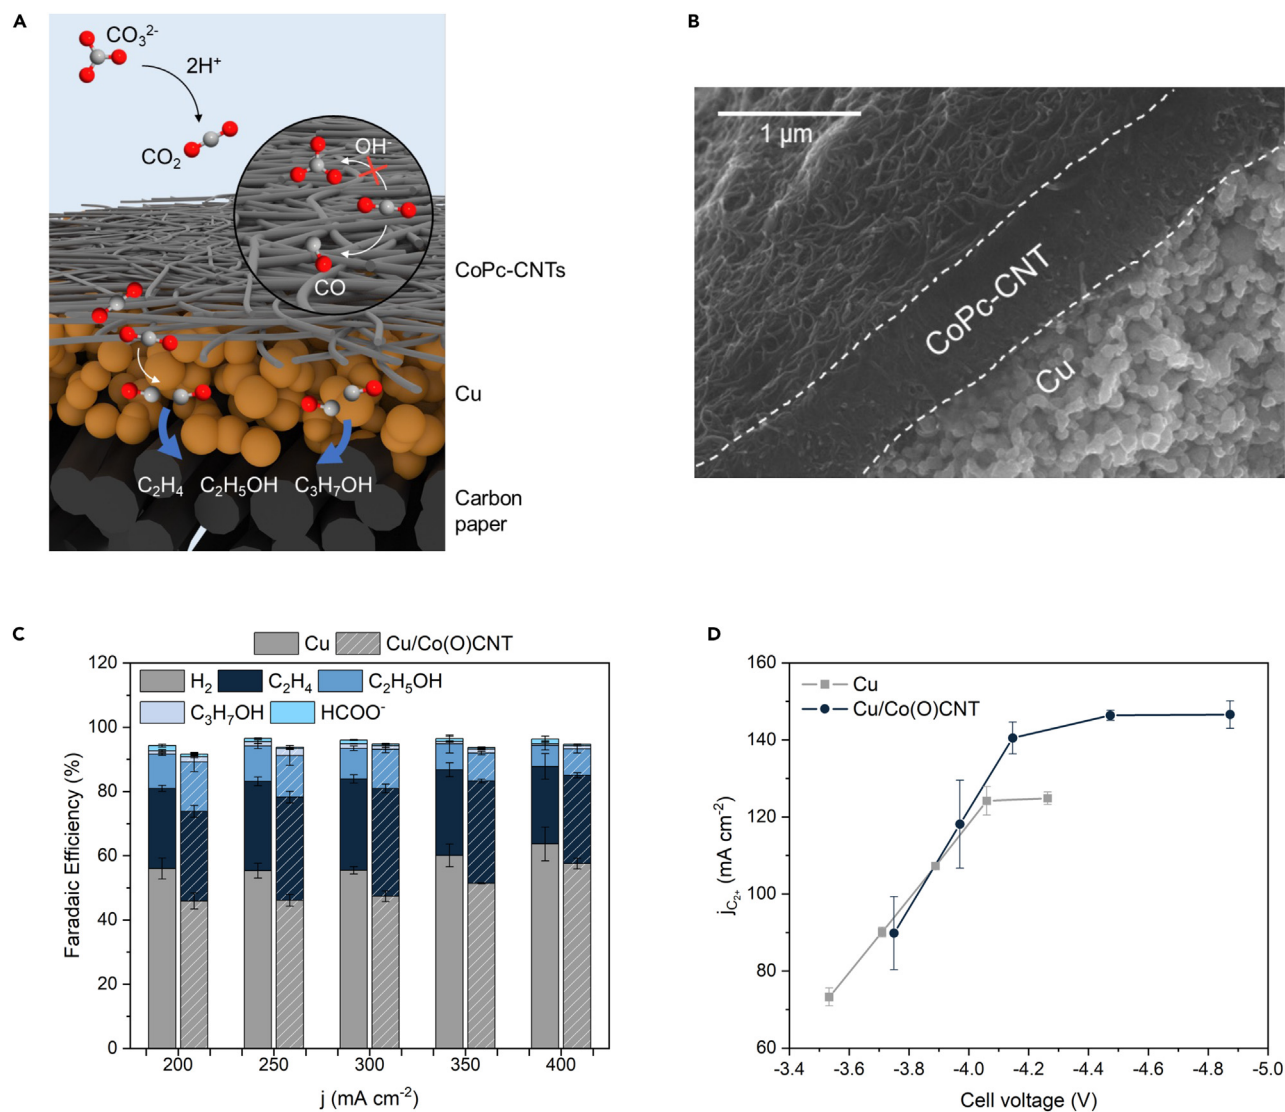

**Figure 3. Electrochemical performance of improved catalyst for carbonate electrolysis**

(A) Illustration of the improved catalyst depositing CoPc-CNTs layer onto Cu electrocatalyst.


(B) Scanning electron microscope image of Cu/CoPc-CNTs layer.

(C) Product distribution of control Cu electrocatalyst and Cu/CoPC-CNTs catalyst at applied current densities from 200 to 400 mA cm<sup>-2</sup>. 1.5 M K<sub>2</sub>CO<sub>3</sub> and 135 μm MCE membranes are used as the electrolyte and interposer, respectively. All experiments were repeated three times to enable reporting of the average and standard error.

(D) C<sub>2+</sub> partial current density vs. full cell voltage for Cu electrocatalyst and Cu/CoPc-CNTs electrocatalyst. All experiments were repeated three times to enable reporting of the average and standard error.

sustained over 20 h (Figure 4B) at the current density of 200 mA cm<sup>-2</sup>, with the C<sub>2+</sub> FE consistently in the range of 36%–42%. The pH of reservoirs remains 11.8 for the absorber, 11.9 for the electrolyte, and 1.8 for the anolyte (Table S7). We found that after 10 h of operation, performance does show a decline (Figure 4B). We studied the cause, finding that the pore structure of the MCE membrane degrades in alkali solution, producing an increase of full cell voltage and hydrogen evolution reactions (HER). It will be important to seek interposer materials that are stable under relevant conditions.



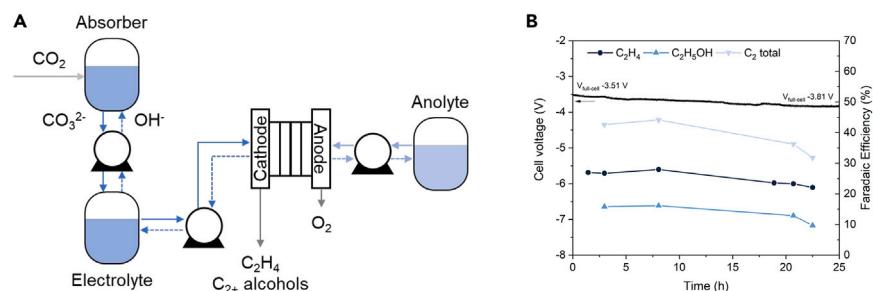

**Figure 4. Extended operation with CO<sub>2</sub> capture liquid stream**

(A) The schematic illustrates the process flow of the capture-and-electrolysis system. CO<sub>2</sub> is captured with 3 M KOH at the absorber until the pH of the solution reaches to ~12, and the capture liquid, K<sub>2</sub>CO<sub>3</sub>, is fed to the electrolyzer. The lean capture liquid, KOH, returns to the absorber.

(B) Long-term operation for the capture-and-electrolysis system. The experiment was performed with a Cu/CoPc-CNTs electrocatalyst and 135 μm interposer. Cell voltage and Faradaic efficiency of C<sub>2</sub>H<sub>4</sub>, C<sub>2</sub>H<sub>5</sub>OH, and C<sub>2+</sub> products are noted during the operation.

### Economic assessments of carbonate electrolysis

In Table 1, we offer an analysis that also estimates energy costs—associated with upstream generation for the gas-phase CO<sub>2</sub> and carbonate capture solutions, electrolysis, separation, and carbonate regeneration—in systems including alkaline CO<sub>2</sub> electrolysis,<sup>31</sup> neutral CO<sub>2</sub> electrolysis in a membrane electrode assembly (MEA),<sup>37</sup> and acidic CO<sub>2</sub> electrolysis<sup>23</sup> vs. this present work (details in Note S8). Both the gaseous CO<sub>2</sub> approaches in alkaline and neutral conditions experience a CO<sub>2</sub> utilization limit (≤25%) since CO<sub>2</sub> gas is lost to carbonate formation, and carbonate crosses over to the anodic side during electrolysis.<sup>19,38</sup> The product gas stream is diluted by unreacted CO<sub>2</sub> for all gas-phase CO<sub>2</sub> approaches. In comparison, the carbonate electrolysis system generates a product stream that does not contain CO<sub>2</sub>.

As is now well-established, alkaline electrolysis leads to a high rate of CO<sub>2</sub> loss—typically 95% is lost to carbonate and unreacted form—leading to an estimated 310 GJ/tonne of C<sub>2</sub>H<sub>4</sub> for regeneration/separation energy costs. This cost is equal to 7× the lower heating value (LHV) of C<sub>2</sub>H<sub>4</sub>.

Neutral CO<sub>2</sub>RR still produces a high CO<sub>2</sub> stream in the cathodic outlet and this necessitates ~60 GJ/tonne of C<sub>2</sub>H<sub>4</sub> investment in CO<sub>2</sub> separation from the cathode. Furthermore, CO<sub>2</sub> crossover mandates a separation of the O<sub>2</sub>-containing stream in the anodic outlet contributing to ~60 GJ/tonne of C<sub>2</sub>H<sub>4</sub> of separation energy cost. The total separation cost is equal to 2× the LHV of C<sub>2</sub>H<sub>4</sub>.

The acidic CO<sub>2</sub>RR system enables an estimated decrease in product separation cost to ~18 GJ/tonne of C<sub>2</sub>H<sub>4</sub> with a high CO<sub>2</sub> utilization efficiency of ~76%. Unlike alkaline and neutral CO<sub>2</sub>RR, no CO<sub>2</sub> is lost as carbonate formation and crossover, eliminating the need for processes to regenerate the carbonate or crossover CO<sub>2</sub>. However, there is a trade-off between FE and CO<sub>2</sub> utilization in presently available acidic CO<sub>2</sub>RR systems,<sup>21,23</sup> with these systems still requiring energy-intensive DAC to generate gaseous CO<sub>2</sub> costing roughly ~28 GJ/tonne of C<sub>2</sub>H<sub>4</sub>.

In contrast, the carbonate electrolysis to the C<sub>2</sub>H<sub>4</sub> system produces a CO<sub>2</sub> concentration that is undetectable in the cathode stream. This obviates the energy needed to separate CO<sub>2</sub> and C<sub>2</sub>H<sub>4</sub>. What remains is 2 GJ/tonne of C<sub>2</sub>H<sub>4</sub> to remove H<sub>2</sub> and H<sub>2</sub>O from the cathodic outlet stream. The low separation cost originates from the high concentration of C<sub>2</sub>H<sub>4</sub> and the absence of CO<sub>2</sub>. Furthermore, the system lowers the upstream generation cost by a factor of ~10 by bypassing the thermal swing of DAC.

We note the need to improve further the energy efficiency of the reactive capture electrolyzer itself. We offer that further studies of *in situ* CO<sub>2</sub> diffusion in the interposer, and further advances in interposer/electrocatalyst design, may contribute toward this goal.

## DISCUSSION

Interposer and catalyst joint design enabled us herein to electroproduce 56 wt % C<sub>2</sub>H<sub>4</sub> from a carbonate solution with no detected CO<sub>2</sub> in the gas stream. To achieve this result, we focused on local pH and reactant concentration as metrics driving the performance of an electrochemical reactive capture system. The carbonate electrolysis system produces a gas stream that is undiluted by CO<sub>2</sub> and accomplishes complete CO<sub>2</sub> utilization, reducing regeneration/separation costs.

## EXPERIMENTAL PROCEDURES

### Resource availability

#### Lead contact

Further information and requests for resources should be directed to and will be fulfilled by the lead contact, Edward Sargent ([ted.sargent@utoronto.ca](mailto:ted.sargent@utoronto.ca)).

#### Materials availability

This study did not generate new unique reagents.

#### Data and code availability

The data presented in this work are available from the corresponding authors upon reasonable request.

### Catalyst preparation

All reagents used in this work were purchased from suppliers without further purification. Cu catalysts (US Research Nanomaterials) were prepared by spray-coating Cu nanoparticle ink onto carbon paper (Freudenberg H23, Fuel Cell Store). Cu nanoparticles (80 mg) were dispersed in a mixture of 12 mL methanol and 160  $\mu$ L Nafion solution and then sonicated for 3 h. The Cu nanoparticle ink was spray-coated on the carbon paper with a loading of  $\sim$ 4 mg/cm<sup>2</sup> and dried under atmospheric conditions. The Cu catalysts were used for electrochemical characterization for carbonate electrolysis in a MEA cell.

For simulated carbonate electrolysis experiments in a flow cell, Cu catalysts were prepared by spray-coating Cu nanoparticles onto a polytetrafluoroethylene (PTFE) substrate (450 nm pore size). Cu nanoparticles (80 mg) were dispersed in a mixture of 12 mL methanol and 160  $\mu$ L Nafion solution and then sonicated for 3 h. The Cu nanoparticle ink was spray-coated on the PTFE substrate with a loading of  $\sim$ 4 mg/cm<sup>2</sup> and dried under atmospheric conditions.

Cobalt phthalocyanines (CoPc), carboxylic acid-functionalized carbon nanotubes (CNTs), and dimethylformamide (DMF) were purchased from Sigma Aldrich and used without further treatment. CoPc-CNTs catalyst was synthesized with modification from the previous report.<sup>35</sup> 30 mg of carboxylic acid-functionalized CNTs were dispersed in DMF (20 mL, solution 1) and sonicated for 1 h. A calculated amount of CoPc was dispersed in DMF (20 mL, solution 2) and sonicated for 1 h. Solutions 1 and 2 were mixed and sonicated for 30 min. After sonication, the mixture solution was stirred for 24 h at room temperature. CoPc-CNTs were centrifuged and washed with DMF, ethanol, and H<sub>2</sub>O, followed by freeze drying to obtain the final catalyst material.

CoPc-CNTs/Cu catalysts were prepared by spray-coating on the prepared Cu/carbon paper. CoPc-CNTs were dispersed in a mixture of 3 mL ethanol and 50  $\mu$ L Nafion solution and then sonicated for 1 h. The CoPc-CNTs nanoparticle ink was spray-coated on the Cu/carbon paper with a loading of  $\sim$ 0.3 mg/cm<sup>2</sup> and dried under atmospheric conditions.

### Electrochemical performance

Electrochemical data were collected using an electrochemical station (PGSTAT204) in an MEA system and a flow cell system. All experiments were repeated three times to enable reporting of the average and standard error. Electrolysis was maintained for at least 30 min prior to collecting gas and liquid samples. For the MEA system with carbonate electrolysis, the as-prepared Cu/carbon paper catalyst was used as the cathode in varying the distances between the cathode and a CEM: 0, 135, 270, and 540  $\mu$ m with MCE membrane and varying catholyte: 0.5, 1, 1.5, and 2 M of K<sub>2</sub>CO<sub>3</sub>. The anolyte was a 0.5 M H<sub>2</sub>SO<sub>4</sub> solution. Titanium foam-supported iridium oxide (IrO<sub>x</sub>/Ti) was used as the anode OER catalyst. Nafion 117 membrane was used to separate the two electrodes. The catholyte and anolyte were circulated using a peristaltic pump.

For the simulated carbonate electrolysis in a flow cell, the as-prepared Cu/PTFE catalyst was used as the working electrode in the catholyte (1.5 M of K<sub>2</sub>CO<sub>3</sub>) in varying gas-phase CO<sub>2</sub> partial pressure in the N<sub>2</sub> stream, maintaining the total flow rate of 50 sccm and gas-phase CO<sub>2</sub> flow rate. The anolyte was always a 1 M KOH solution. Ni foam and 3 M Ag/AgCl were used as the anode and reference electrodes, respectively. An anion exchange membrane (Fumasep FAA-3-PK-130) was used to separate the cathode and the anode. The catholyte and anolyte were circulated using a peristaltic pump.

The gas-phase products were analyzed using GC (Shimadzu 2014, PerkinElmer Clarus 580) equipped with a thermal conductivity detector (TCD) and a flame ionization detector (FID). All measurements were repeated three times to report the average and standard error. The liquid phase products were analyzed with a 600 MHz Agilent DD2 <sup>1</sup>H NMR.

The detection limit of GC for gas-phase products (CO and CH<sub>4</sub>) is measured by varying the concentration of gas in the CO<sub>2</sub> stream. The ppm level of the gas-phase product is injected three times. The area of a peak is linearly correlated to the concentration when the area value is plotted at the y axis, and the concentration is at the x axis. The intercept of the x axis represents the detection limits of gas concentration. The detection limit of CO<sub>2</sub> is measured by injecting a different air volume from 1 to 5 mL. The CO<sub>2</sub> concentration in the air is assumed at 400 ppm.

### Material characterization

The Cu/CoPc-CNTs catalyst morphology was characterized by field emission SEM (Hitachi, SU5000). The surface composition was analyzed with ThermoFisher Scientific K-alpha XPS using Al K $\alpha$  X-ray radiation. XPS spectra were calibrated with the C 1s peak at 284.5 eV. SEM-EDS was conducted by JEOL JSM-7900FLV SEM at an accelerating voltage of 10 kV with backscattered electron detection, which is equipped with a light-element X-ray detector and an Oxford Aztec energy-dispersive X-ray analysis system.

### Fluorescence measurements

For the simulated interposer system in a H-cell, a carbon paper, Pt mesh, and Ag/AgCl reference electrode were used as the working, counter, and reference electrodes, respectively. 0.2 M K<sub>2</sub>CO<sub>3</sub> and 0.5 M H<sub>2</sub>SO<sub>4</sub> electrolytes were used as a catholyte and an anolyte, respectively. Nafion 117 membrane was used to separate the cathode

part and the anode part. Molecular Probes LysoSensor Green DND 189 (LSG) was used to measure a pH range of 1–6, and 5(6)-carboxynaphthofluorescein (CNF) was used to measure neutral and alkaline pH from 6 to 14. Using 365 nm of UV light, the fluorescence emissions were collected with a spectrometer (Ocean Optics, QE Pro).

### Stability test

Two reservoirs were connected by peristaltic pumps (Figure S17). CO<sub>2</sub> is purged into the absorber with 3 M KOH until the pH of the solution reaches to ~12, and an electrolyte reservoir provides the carbonate solution to the electrolyzer. The carbonate electrolyte is pumped to the MEA cell with no gas purging. The regenerated KOH solution returns to the absorber, where it captures CO<sub>2</sub> in the form of CO<sub>3</sub><sup>2-</sup>. The gas products from the electrolyte reservoir were monitored with GC injection.

### SUPPLEMENTAL INFORMATION

Supplemental information can be found online at <https://doi.org/10.1016/j.joule.2023.05.003>.

### ACKNOWLEDGMENTS

This work was financially supported by the Ontario Research Foundation: Research Excellence Program, the Natural Sciences and Engineering Research Council (NSERC) of Canada. H.L. and E.S. acknowledge the financial support from Northwestern University's start-up grant.

### AUTHOR CONTRIBUTIONS

E.S. supervised the work. G.L. contributed to the main idea and designed experiments. A.S.R. contributed to multiphysic modeling. B.-H.L. fabricated the electrocatalyst and contributed to material characterization. J.Z., D.H.W., and Y.C.X. contributed to the electrochemical experiments. J.P.E. and Y.Z. performed the energy analysis. M.G.L. conducted C13 labeling experiments. E.D.J. conducted local pH measurements. J.A., S.P., and H.L. conducted material characterization. F.A. performed voltage breakdown analysis. T.A. and S.L. assisted in the multiphysic modeling. I.G., R.K.M., R.D., C.P.O., Z.C., and D.S. contributed to data analysis and manuscript preparation.

### DECLARATION OF INTERESTS

The authors declare no competing interests.

Received: January 20, 2023

Revised: May 3, 2023

Accepted: May 4, 2023

Published: May 26, 2023

### REFERENCES

- Brethomé, F.M., Williams, N.J., Seipp, C.A., Kidder, M.K., and Custelcean, R. (2018). Direct air capture of CO<sub>2</sub> via aqueous-phase absorption and crystalline-phase release using concentrated solar power. *Nat. Energy* 3, 553–559. <https://doi.org/10.1038/s41560-018-0150-z>.
- Kätelhön, A., Meys, R., Deutz, S., Suh, S., and Bardow, A. (2019). Climate change mitigation potential of carbon capture and utilization in the chemical industry. *Proc. Natl. Acad. Sci. USA* 116, 11187–11194. <https://doi.org/10.1073/pnas.1821029116>.
- Socolow, R., Desmond, M., Aines, R., Blackstock, J., Bolland, O., Kaarsberg, T., Lewis, N., Mazzotti, M., Pfeffer, A., and Sawyer, K. (2011). Direct air capture of CO<sub>2</sub> with chemicals: a technology assessment for the APS panel on public affairs (American Physical Society). <http://www.aps.org/policy/reports/assessments/upload/dac2011.pdf>.
- Lee, G., Li, Y.C., Kim, J.-Y., Peng, T., Nam, D.-H., Sedighian Rasouli, A., Li, F., Luo, M., Ip, A.H., Joo, Y.-C., et al. (2021). Electrochemical upgrade of CO<sub>2</sub> from amine capture solution. *Nat. Energy* 6, 46–53. <https://doi.org/10.1038/s41560-020-00735-z>.
- Li, Y.C., Lee, G., Yuan, T., Wang, Y., Nam, D.-H., Wang, Z., García de Arquer, F.P., Lum, Y., Dinh, C.-T., Voznyy, O., et al. (2019). CO<sub>2</sub> electroreduction from carbonate electrolyte. *ACS Energy Lett.* 4,

- 1427–1431. <https://doi.org/10.1021/acscenergylett.9b00975>.
- Li, T., Lees, E.W., Goldman, M., Salvatore, D.A., Weekes, D.M., and Berlinguette, C.P. (2019). Electrolytic conversion of bicarbonate into CO in a flow cell. *Joule* 3, 1487–1497. <https://doi.org/10.1016/j.joule.2019.05.021>.
  - Zhang, Z., Lees, E.W., Habibzadeh, F., Salvatore, D.A., Ren, S., Simpson, G.L., Wheeler, D.G., Liu, A., and Berlinguette, C.P. (2022). Porous metal electrodes enable efficient electrolysis of carbon capture solutions. *Energy Environ. Sci.* 15, 705–713. <https://doi.org/10.1039/D1EE02608A>.
  - Xiao, Y.C., Gabardo, C.M., Liu, S., Lee, G., Zhao, Y., O'Brien, C.P., Miao, R.K., Xu, Y., Edwards, J.P., and Fan, M. (2023). Direct carbonate electrolysis into pure syngas. *EES Catal.* 1, 54–61.
  - Kar, S., Goeppert, A., and Prakash, G.K.S. (2019). Integrated CO<sub>2</sub> capture and conversion to formate and methanol: connecting two threads. *Acc. Chem. Res.* 52, 2892–2903. <https://doi.org/10.1021/acs.accounts.9b00324>.
  - Kothandaraman, J., Saavedra Lopez, J., Jiang, Y., Walter, E.D., Burton, S.D., Dagle, R.A., and Heldebrant, D.J. (2021). Integrated capture and conversion of CO<sub>2</sub> to methane using a water-lean, post-combustion CO<sub>2</sub> capture solvent. *ChemSusChem* 14, 4812–4819. <https://doi.org/10.1002/cssc.202101590>.
  - Sen, R., Goeppert, A., Kar, S., and Prakash, G.K.S. (2020). Hydroxide based integrated CO<sub>2</sub> capture from air and conversion to methanol. *J. Am. Chem. Soc.* 142, 4544–4549. <https://doi.org/10.1021/jacs.9b12711>.
  - GlobeNewswire. PrecedenceResearch (2021). Ethanol market size worth around USD 155.6 billion by 2030. t. <https://www.globenewswire.com/news-release/2021/01/18/2160198/0/en/Ethanol-Market-Size-Worth-Around-USD-155-6-Billion-by-2030.html#:~:text=The%20global%20ethanol%20market%20size,5.2%25%20from%202021%20to%202030.>
  - Polaris Market Research (2021). Ethylene market size worth \$230.7 billion by 2029|CAGR: 5.5%. <https://www.polarismarketresearch.com/press-releases/ethylene-market>.
  - Polaris Market Research (2017). Feed acidifiers market size worth \$2.03 billion by 2026|CAGR: 4.5%. <https://www.polarismarketresearch.com/press-releases/feed-acidifiers-market>.
  - Polaris Market Research (2021). Carbon dioxide market size worth \$9.91 billion by 2029|CAGR: 4.1%. <https://www.polarismarketresearch.com/press-releases/carbon-dioxide-co2-market>.
  - Keith, D.W., Holmes, G., St. Angelo, D., and Heidel, K. (2018). A process for capturing CO<sub>2</sub> from the atmosphere. *Joule* 2, 1573–1594. <https://doi.org/10.1016/j.joule.2018.05.006>.
  - García de Arquer, F.P.G.d., Dinh, C.T., Ozden, A., Wicks, J., McCallum, C., Kirmani, A.R., Nam, D.H., Gabardo, C., Seifitokaldani, A., Wang, X., et al. (2020). CO<sub>2</sub> electrolysis to multicarbon products at activities greater than 1 A cm<sup>-2</sup>. *Science* 367, 661–666. <https://doi.org/10.1126/science.aay4217>.
  - Li, F., Thevenon, A., Rosas-Hernández, A., Wang, Z., Li, Y., Gabardo, C.M., Ozden, A., Dinh, C.T., Li, J., Wang, Y., et al. (2020). Molecular tuning of CO<sub>2</sub>-to-ethylene conversion. *Nature* 577, 509–513. <https://doi.org/10.1038/s41586-019-1782-2>.
  - Rabinowitz, J.A., and Kanan, M.W. (2020). The future of low-temperature carbon dioxide electrolysis depends on solving one basic problem. *Nat. Commun.* 11, 5231.
  - Alerte, T., Edwards, J.P., Gabardo, C.M., O'Brien, C.P., Gaona, A., Wicks, J., Obradović, A., Sarkar, A., Jaffer, S.A., MacLean, H.L., et al. (2021). Downstream of the CO<sub>2</sub> electrolyzer: assessing the energy intensity of product separation. *ACS Energy Lett.* 6, 4405–4412. <https://doi.org/10.1021/acscenergylett.1c02263>.
  - Huang, J.E., Li, F., Ozden, A., Sedighian Rasouli, A., García de Arquer, F.P., Liu, S., Zhang, S., Luo, M., Wang, X., Lum, Y., et al. (2021). CO<sub>2</sub> electrolysis to multicarbon products in strong acid. *Science* 372, 1074–1078. <https://doi.org/10.1126/science.abg6582>.
  - O'Brien, C.P., Miao, R.K., Liu, S., Xu, Y., Lee, G., Robb, A., Huang, J.E., Xie, K., Bertens, K., Gabardo, C.M., et al. (2021). Single pass CO<sub>2</sub> conversion exceeding 85% in the electrosynthesis of multicarbon products via local CO<sub>2</sub> regeneration. *ACS Energy Lett.* 6, 2952–2959. <https://doi.org/10.1021/acscenergylett.1c01122>.
  - Zhao, Y., Hao, L., Ozden, A., Liu, S., Miao, R.K., Ou, P., Alkayali, T., Zhang, S., Ning, J., Liang, Y., et al. (2023). Conversion of CO<sub>2</sub> to multicarbon products in strong acid by controlling the catalyst microenvironment. *Nat. Synth.* <https://doi.org/10.1038/s44160-022-00234-x>.
  - Gabardo, C.M., O'Brien, C.P., Edwards, J.P., McCallum, C., Xu, Y., Dinh, C.-T., Li, J., Sargent, E.H., and Sinton, D. (2019). Continuous carbon dioxide electroreduction to concentrated multi-carbon products using a membrane electrode assembly. *Joule* 3, 2777–2791. <https://doi.org/10.1016/j.joule.2019.07.021>.
  - Kim, C., Bui, J.C., Luo, X., Cooper, J.K., Kusoglu, A., Weber, A.Z., and Bell, A.T. (2021). Tailored catalyst microenvironments for CO<sub>2</sub> electroreduction to multicarbon products on copper using bilayer ionomer coatings. *Nat. Energy* 6, 1026–1034. <https://doi.org/10.1038/s41560-021-00920-8>.
  - Idem, R., Supap, T., Shi, H., Gelowitz, D., Ball, M., Campbell, C., and Tontiwachwuthikul, P. (2015). Practical experience in post-combustion CO<sub>2</sub> capture using reactive solvents in large pilot and demonstration plants. *Int. J. Greenhouse Gas Control* 40, 6–25. <https://doi.org/10.1016/j.jggc.2015.06.005>.
  - Lin, Y.-J., and Rochelle, G.T. (2016). Approaching a reversible stripping process for CO<sub>2</sub> capture. *Chem. Eng. J.* 283, 1033–1043. <https://doi.org/10.1016/j.cej.2015.08.086>.
  - Greenblatt, J.B., Miller, D.J., Ager, J.W., Houle, F.A., and Sharp, I.D. (2018). The technical and energetic challenges of separating (photo) electrochemical carbon dioxide reduction products. *Joule* 2, 381–420. <https://doi.org/10.1016/j.joule.2018.01.014>.
  - Lees, E.W., Bui, J.C., Song, D., Weber, A.Z., and Berlinguette, C.P. (2022). Continuum model to define the chemistry and mass transfer in a bicarbonate electrolyzer. *ACS Energy Lett.* 7, 834–842. <https://doi.org/10.1021/acscenergylett.1c02522>.
  - Kas, R., Yang, K., Yewale, G.P., Crow, A., Burdyny, T., and Smith, W.A. (2022). Modeling the local environment within porous electrode during electrochemical reduction of bicarbonate. *Ind. Eng. Chem. Res.* 61, 10461–10473. <https://doi.org/10.1021/acs.iecr.2c00352>.
  - Dinh, C.T., Burdyny, T., Kibria, M.G., Seifitokaldani, A., Gabardo, C.M., García de Arquer, F.P., Kiani, A., Edwards, J.P., De Luna, P., Bushuyev, O.S., et al. (2018). CO<sub>2</sub> electroreduction to ethylene via hydroxide-mediated copper catalysis at an abrupt interface. *Science* 360, 783–787. <https://doi.org/10.1126/science.aas9100>.
  - Varela, A.S., Kroschel, M., Reier, T., and Strasser, P. (2016). Controlling the selectivity of CO<sub>2</sub> electroreduction on copper: the effect of the electrolyte concentration and the importance of the local pH. *Cat. Today* 260, 8–13. <https://doi.org/10.1016/j.cattod.2015.06.009>.
  - Jouny, M., Luc, W., and Jiao, F. (2018). General techno-economic analysis of CO<sub>2</sub> electrolysis systems. *Ind. Eng. Chem. Res.* 57, 2165–2177. <https://doi.org/10.1021/acs.iecr.7b03514>.
  - Shin, H., Hansen, K.U., and Jiao, F. (2021). Techno-economic assessment of low-temperature carbon dioxide electrolysis. *Nat. Sustain.* 4, 911–919. <https://doi.org/10.1038/s41893-021-00739-x>.
  - Zhang, X., Wang, Y., Gu, M., Wang, M., Zhang, Z., Pan, W., Jiang, Z., Zheng, H., Lucero, M., Wang, H., et al. (2020). Molecular engineering of dispersed nickel phthalocyanines on carbon nanotubes for selective CO<sub>2</sub> reduction. *Nat. Energy* 5, 684–692. <https://doi.org/10.1038/s41560-020-0667-9>.
  - Li, F., Li, Y.C., Wang, Z., Li, J., Nam, D.-H., Lum, Y., Luo, M., Wang, X., Ozden, A., Hung, S.-F., et al. (2020). Cooperative CO<sub>2</sub>-to-ethanol conversion via enriched intermediates at molecule–metal catalyst interfaces. *Nat. Catal.* 3, 75–82. <https://doi.org/10.1038/s41929-019-0383-7>.
  - Ozden, A., Li, F., García de Arquer, F.P., Rosas-Hernández, A., Thevenon, A., Wang, Y., Hung, S.-F., Wang, X., Chen, B., Li, J., et al. (2020). High-rate and efficient ethylene electrosynthesis using a catalyst/promoter/transport layer. *ACS Energy Lett.* 5, 2811–2818. <https://doi.org/10.1021/acscenergylett.0c01266>.
  - Mardle, P., Cassegrain, S., Habibzadeh, F., Shi, Z., and Holdcroft, S. (2021). Carbonate ion crossover in zero-gap, KOH anolyte CO<sub>2</sub> electrolysis. *J. Phys. Chem. C* 125, 25446–25454. <https://doi.org/10.1021/acs.jpcc.1c08430>.